

## Nanomaterials and Dispersion

### 1. Introduction

Nanomaterials have drawn a great interest and been one of major research thrust in recent years. Nanotechnology, its products and applications have the potential to offer significant social and environmental benefits. The nanomaterials potentially can enhance the materials properties because of the following two aspects: large relative surface area and new quantum effects. Nanomaterials have a much greater surface area to volume ratio than their conventional forms, which can lead to greater chemical reactivity or heat resistance and affect their strength. Also at the nano scale, quantum effects can become much more important in determining the materials properties and characteristics, leading to novel optical, electrical and magnetic behaviors.

The nanomaterials have been applied in many commercial products. The range of commercial products available today is very broad, including stain-resistant and wrinkle-free textiles, cosmetics, sunscreens, electronics, paints and varnishes. Nanocoatings and nanocomposites are finding uses in diverse consumer products, such as windows, sports equipment, bicycles and automobiles. There are novel UV-blocking coatings on glass bottles which protect beverages from damage by sunlight, and longer-lasting tennis balls using butyl-rubber/nano-clay composites. Nanoscale titanium dioxide, for instance, is finding applications in cosmetics, sun-block creams and self-cleaning windows, and nanoscale silica is being used as filler in a range of products, including cosmetics and dental fillings.

Innovations in nanomaterials are also driving advances in battery technology by increasing capacity, improving cyclability, and enhancing rate capability and mechanical toughness. In medicine, proposed uses for nanomaterials include drug delivery, imaging, and the formation of bone composites [1-4]. Additionally, companies in the food and cosmetics industries have incorporated nanomaterials to enhance the quality of their products [5].

Excepting the commercial products, defense and engineering scientists have shown that nanomaterials are potentially useful in electronics, sensors, munitions, and energetic/reactive systems involved with the advancement of propulsion technology [6].

### 2. Classification of nanomaterials

Nanomaterials could be the single phase materials and multi-phase composites. The single nano phase materials are generally nanoparticle with particle size less than 100 nm in at least one dimension. The single phase nanomaterials could also be bulk materials consisting of nanoparticle aggregate, cluster, or agglomerate. In this case, the expected properties may not be reached because of the agglomeration. In order to achieve the better properties and performance, the aggregated nanoparticles are needed to be separated and dispersed.

Multi-phase nanocomposites are materials by adding nano phase materials into the matrices. These composites are most based on polymer matrices. By incorporating nanomaterials into existing products, they enhance certain properties or provide new functionalities, such as increased strength, improved heat or chemical resistance, better conductivity, etc. For example, higher performance polymeric composites contain 6-8  $\mu\text{m}$ -diameter graphite fibers. However, the enhanced physical and mechanical properties of multi-phase composite materials depend on nanoparticles to be fully dispersed them at small length scales.

### **3. Important of uniform dispersion of nano phase**

The microstructure uniformity is of paramount importance to the bulk materials' properties and performance. The agglomeration of nanoparticles is a very significant, spontaneous phenomenon. Uncontrolled agglomeration of powders due to attractive van der Waals forces can give rise to in microstructural inhomogeneities which result in the desired properties damaged.

The strong tendency of nanoparticles to form clumps and clusters ("agglomerates") is a serious technological problem that impedes the effective use of nanoparticles in many applications. For example, the nanoclay aggregates (as large as  $10\mu\text{m}$ ) could result in reduction of strength [7-8] in nanoclay/epoxy composites.

Therefore the nanomaterials uniform dispersion inside the matrix is a research thrust. Effective means of deagglomerating and dispersing are needed to overcome the bonding forces after wetting the powder.

### **4. Dispersion process**

#### **4.1 Single nano phase materials**

In case of single nano phase materials, the separation and dispersion of nanomaterials is by means of repulsive interparticle forces to prevent agglomeration.

In case of solid nanoparticles, The dispersion process for single nano phase materials generally doesn't through grinding method. The basic strategy is by surface modification to separate them since the surface modification can minimize the agglomeration by decreasing the particle surface energy.

For a solution, two methods are commonly used. **The first method** provides the dispersion by electrostatic repulsion. The repulsion results form the interactions between the electric double layers surrounding the particles. An unequal charge distribution always exists between a particle surface and the solvent. Electrostatic stabilization of dispersion occurs when the electrostatic repulsive force overcomes the attractive van der Waals force between the particles. This stabilization method is generally effective in dilute systems of aqueous or polar organic media. This method is very sensitive to the electrolyte concentration since a change in the concentration may destroy the electric double layer which will result in particle agglomeration. **The second method** of

stabilization involves the steric forces. Surfactant molecules can adsorb onto the surface of particles and their lyophilic chains will then extend into the solvent the interact with each other. The solvent-chain interaction, which is a mixing effect, increases the free energy of the system and produces an energy barrier to the closer approach of particles. When the particles come into closer contact with each other, the motion of the chains extending into the solvent become restricted and produce an entropic effect. Steric stabilization can occur in the absence of the electric barriers. Steric stabilization is effective in both aqueous and non-aqueous media, and is less sensitive to impurities or trace additives than electric stabilization. The steric stabilization method is particularly effective in dispersing high concentrations of particles.

Some additives, which can be used to disperse the nanoparticles, are useful but also present their own problems, especially in regard to the purity of the final product.

#### **4.2 Multi-phase nanocomposites**

The utilization of nanometer scale particulates such as carbon nanotubes and nanoclay into polymers is increasing due to potential improvements in thermo-physical properties. For instance, researchers at the Toyota Research Labs observed up to 60% increase in strength of nylon 6 sample with the addition of nanoclay. Similarly, Chen et al., fabricated nanocomposite samples by melt-compounding nanoclay with maleic anhydride modified polypropylene at loadings up to 50%. The authors observed monotonic improvements in tensile strength and stiffness, reaching 120% and 400%, respectively. However, the nanoclay aggregates (as large as 10 $\mu$ m) could result in reduction of strength [7].

However, large macro-particles or cluster are detrimental to the properties of the composite materials since, they: (1) tend to have various types of defects at the atomic or molecular level, (2) may contain voids or impurities, (3) facilitate ineffective load transfer at the interface due to their usually irregular shape. For such cases, mixing nanomaterials into other materials, whether they are polymeric or metallic, may degrade some of the original material properties.

Various proposed dispersion methods include (1) directly mixing nanomaterials with a polymer either in the solid or liquid form by a mechanical mixer, (2) using a sonicator or ultrasonic energy to enhance dispersion, (3) using an electric field after mechanical mixing to enhance dispersion (applying AC or DC voltage at various levels has been tried), (4) solid state mixing such as grinding nanomaterials and polymer together at room temperature, (5) mixing with a polymer during melting in the extruder before the extrusion or molding process (this method benefits from the high shear forces generated in an extruder to enhance dispersion), (6) cryo-mixing or mixing at very low temperatures to make the polymer brittle enough so that polymer particles can be mixed with nanomaterials at a smaller length scale, and (7) heating the polymer to higher temperatures to decrease the viscosity of the polymer to enhance the mixing.

Various mixing technologies, which are the commonly employed strategy, are available for the efficient processing of products containing nanomaterials depending on rheology and shear requirements [9].

**Low-Viscosity Nanodispersions.** The dispersion of nanomaterials into a low-viscosity formulation typically involves a pre-mix stage to combine the raw materials. This is done with the use of low-speed propellers, turbines, or simple agitators. Due to attractive forces between the individual nanoparticles, they combine with the liquid vehicle in the form agglomerates. High shear forces are necessary to break up these groups of agglomerates. How aggressive those shear forces need to be can vary from one formulation to another. One proven method is the use of Ross Ultra-High Shear Mixers, specially engineered rotor/stator devices that run at extremely high Ross MegaShear used for dispersing and tip speeds up to 11,000 fpm.

**Medium-Viscosity Nanodispersions.** Higher loadings of nanoparticles can result in a premix of substantial viscosity, rendering single-shaft devices inadequate. For these requirements, a multi-shaft mixing system is recommended wherein two or more independently-driven agitators work in tandem such as a low-speed anchor agitator, a saw-tooth disperser blade and a rotor/stator assembly equipped for powder induction. This configuration provides a unique combination of laminar bulk flow, high shear mixing, dust-free sub-surface powder addition, deagglomeration and superior heat transfer. After a batch cycle, the nanodispersions may be further polished by running it through an Ultra-High Shear Mixer.

**High-Viscosity Nanodispersions.** As product viscosity continues to build up, a multi-shaft mixing system will eventually fail to produce adequate flow. When agitators with a fixed axis of rotation no longer suffice, a move to a planetary mixer is required. The agitators of a planetary mixer rotate and travel through the mix vessel by passing through every point within the batch – regardless of product rheology. Examples are the classic Double Planetary Mixer (DPM) and “hybrid” planetary mixers featuring one or two stirrer blades (similar to those in a DPM) supplemented by one or two high speed disperser shafts which also revolve on their own axes while orbiting the mix vessel. For example, a three roll mill has been used to mix nanoclay into epoxy [10] matrix.

## 6. Application Examples

### 6.1 Silver particle dispersion

The comparison of mechanical mixing with a three-roller mill and sonication are conducted to disperse the nanosized silver particles in ethylene glycol. The measurement results show that mixing with a three-roll mill is an effective tool to break the agglomerates of silver nanoparticles in solvent, resulting in a better dispersion [11].

A uniform dispersion of silver nanoparticles into a binder solution is also achieved in a Ross Double Planetary Mixer under vacuum. After mixing, the paste is fed into a Ross Three Roll Mill, a kind of mill providing high shear force, to break down any agglomerates. The milled material exhibits a markedly glossier, more homogenous appearance indicating an improvement in dispersion quality.

## 6.2 Nanocomposites with carbon nanotubes

Polymer matrix nanocomposites with filler such as carbon fiber, fiber glass or other polymer fibers render high mechanical properties, high electrical conductivity, high electrostatic discharge, high electromagnetic interference, and high thermal conductivity, with which the regular polymer can't provide. Carbon nanotubes have high mechanical properties from their high aspect ration, high electrical conductivity, high thermal conductivity, and high thermal stability. By adding carbon nanotube into the polymer, it is potential to improve the polymer matrix in terms of solvent resistance, stiffness, glass transition temperature (Tg) and reduce thermal shrinkage. However, it requires a high loading (about 10 to 25 wt%) and a good dispersion to reach the desired polymer properties. The smooth sidewall surface of carbon nanotube, that is incompatible with most solvents and polymers, results in poor dispersion of carbon nanotube in polymer matrixes.

However, the potential of using nanotubes as a constituent of polymer composites has not been presently realized mainly because of the difficulties associated with dispersion and processing. High aspect ratio, combined with high flexibility, increase the possibility of nanotube entanglement and close packing. The low dispersity comes from the tendency of pristine nanotubes to assemble into bundles or ropes like shown in Fig. 1 [12]. Thus, a significant challenge in developing high-performance CNT-polymer composites is to introduce the individual CNTs in a polymer matrix in order to achieve better dispersion and alignment and strong interfacial interactions, to improve the load and electron transfer across the CNT-polymer matrix interfaces.

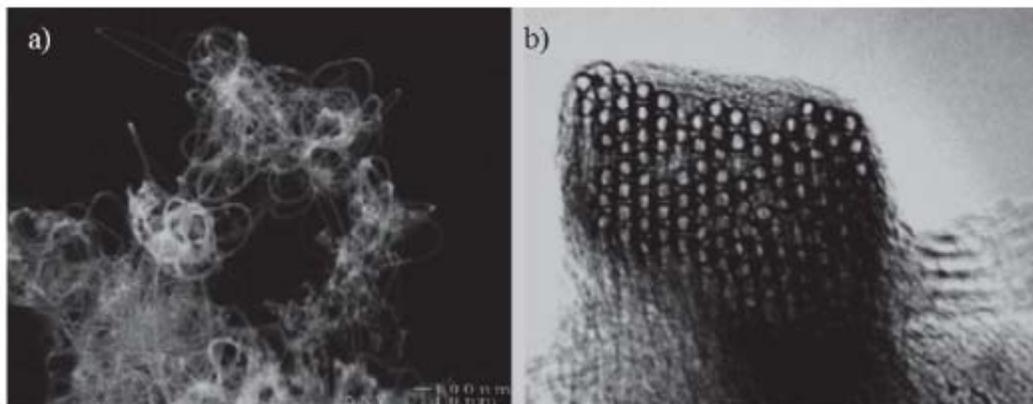


Fig. 1 (a) SEM image of entangled SWCNT agglomerates and (b) TEM image of a SWCNT bundle [12].

Here we compare the most commonly employed methods listed in part 4.2 (1), (2), and (4) for CNT dispersion [13] .

Ball milling is a method that is usually used to grind bulk materials into fine powder. During milling, a high pressure is generated locally due to the collision between the rigid balls in a sealed container (Fig. 2). Cascading effect of balls reduces the size of material

to fine powder. Balls are usually made by ceramic, flint pebbles and stainless steel. Ball milling has been successfully applied to CNT dispersion into polymer matrices. To obtain narrow length and diameter distributions of CNTs and to open the nanotubes for improved sorption capacity for gases, ball-milling is a very useful method [14]. However, it has also been observed that a large amount of amorphous carbon is created which clearly indicates that the tubes are damaged in different ways and that ballmilling is a destructive method [15].

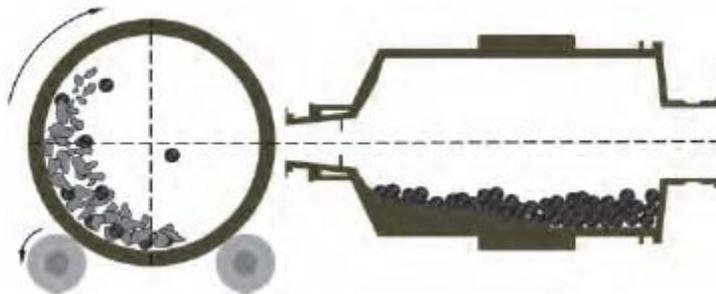


Fig. 2 Schematics of ball milling technique

Ultrasonication is a very effective method of dispersion and deagglomeration of CNTs, as ultrasonic waves of high-intensity ultrasound generates cavitation in liquids (Fig. 3 ). Ultrasonication disperses solids primarily through a microbubble nucleation and collapse sequence. Ultrasonication of fluids leads to three physical mechanisms: cavitation of the fluid, localized heating, and the formation of free radicals. Cavitation, the formation and implosion of bubbles, can cause dispersion But it also damages the CNT structure. Another study showed hardness deteriorated in hardness for sonication greater than 10 minutes [7]

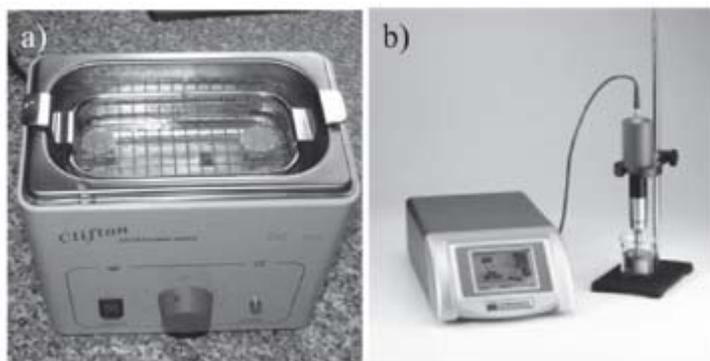


Fig. 3 (a) Bath type, (b) horn type sonicator

Calendering, also commonly known as three-roll-milling (Fig. 4 ) is a dispersion technique that employs both shear flow and extensional flow created by rotating rolls of different speed to mix and disperse CNTs or other nanoscale fillers into polymers or other viscous matrixes. The first and third rollers (usually called the feed and apron rolls, respectively) in Fig. 5 (b) rotate in the same direction while the center roller rotates in the

opposite direction. In order to create high shear rates, angular velocity of the center roll must be higher than that of feed roll ( $\omega_2 > \omega_1$ ). As the resin suspension is fed into the narrow gap ( $\delta$ ) between feed and center rolls, the liquid mixture flows down covering (essentially coating) the adjacent rolls through its surface tension under intensive shear forces. At the end of each subsequent intended dwell time, the processed resin suspension is collected by using a scraper blade in contact with the apron roll. This milling cycle can be repeated several times to maximize dispersion.

One of the unique advantages of this technique is that the gap width between the rollers can be mechanically or hydraulically adjusted and maintained, thus it is easy to obtain a controllable and narrow size distribution of particles in viscous materials. In some operations, the width of gaps can be decreased gradually to achieve the desired level of particle dispersion [16].

Due to the powerful shearing forces of the three roll mill, the dispersion of the agglomerates for the carbon nanotubes is ideal. The carbon nanotubes remain undamaged and the requisite high aspect ratio (length to diameter) is retained. The surface area of the carbon nanotubes wet by epoxy resin continues to grow. As a result, the viscosity rises steadily from 10 cPoise to as much as 100.000 cPoise [17].

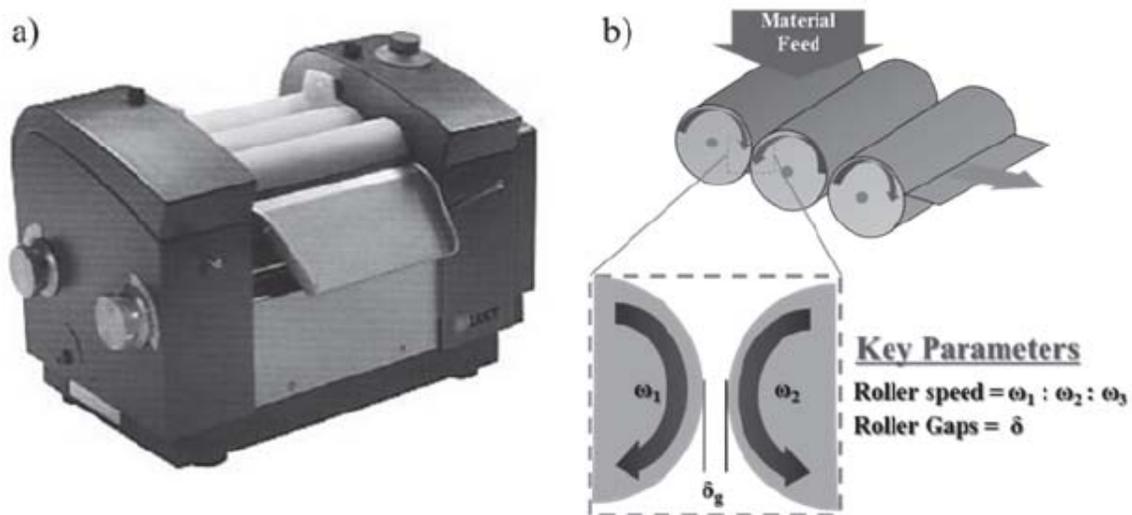


Fig. 4 (a) Calendaring machine (three-roll mill) used for CNT dispersion into a polymer matrix and (b) general schematic diagram of its mechanism.

## 7. Conclusion

Dispersion the nanoparticles is an important topic both in academic research and industrial application. Generally, grinding method is only used for part of nanocomposites. Three-roll mill machine is a very appealing process and benefits the

environment by eliminating the solvent. The three roll mill is an extremely effective dispersion route for nanocomposites containing fiber like filler like carbon fiber, glass fiber, carbon nanotube etc. The mixer can reach a higher degree of intercalation/exfoliation within a short period of time. The main reason is that the high shear force from three roll mill could disperse the fiber-like with great effect.

#### Reference:

1. Kim, D., Zhang, Y., Voit, W., Rao, K., Kehr, J., Bjelke, B., and Muhammed, M. (2001). Superparamagnetic iron oxide nanoparticles for bio-medical applications. *Scripta Mater* 44, 1713–1717
2. Murugan, R., and Ramakrishna, S. (2005). Development of nanocomposites for bone grafting. *Composites Sci. Technol.* 65, 2385–2406
3. Sinha, V., and Trehan, A. (2003). Biodegradable microspheres for protein delivery. *J. Control. Release* 90, 261–280
4. Wu, Y., Yang, W., Wang, C., Hu, J., and Fu, S. (2005). Chitosan Nanoparticles as a novel delivery system for ammonium glycyrrhizinate. *Int. J. Pharm.* 295, 235–245
5. Nanomaterials in personal care products and FDA regulation. The International Center for Technology Assessment. Available at: [www.icta.org/doc/HBA\\_NYC\\_9\\_06\\_Nano\\_in\\_Personal\\_Care\\_Products.pdf](http://www.icta.org/doc/HBA_NYC_9_06_Nano_in_Personal_Care_Products.pdf). 13 September 2006
6. S.P. Ringer and K.R. Ratinac, On the role of characterization in the design of interfaces in nanoscale materials technology. *Microsc. Microanal.* 2004, 10, 324–335
7. Lam C. K., Cheung H.Y, Lau K. T., Zhou L. M., Ho M. W, and Hui D., 2005, Cluster Size Effect in Hardness of Nanoclay/Epoxy Composites, *Composites Part B-Engineering*, 36, pp. 263-269
8. Konstantin Sobolev, Ismael Flores, Roman Hermosillo, Leticia M. Torres-Martinez, Nanomaterials and nanotechnology for high-performance cement composites, *Proceedings of ACI Session on "Nanotechnology of Concrete: Recent Developments and Future Perspectives" November 7, 2006, Denver, USA 91*
9. Christine Banaszek, Mixing Nanomaterials, *Ceramic Industry*, 2010, Nov. 1, pp. 9-12
10. Yasmin A., Abot J. L., and Daniel I. M., 2003, "Processing of caly/epoxy nanocomposites with a three-roll mill machine," *Materials Research Society Symposium Proceedings*, 740, pp. 13.7.1-13.7.6
11. Hung-Wen Lin, Wen-Hwa Hwu, Ming-Der Ger, The dispersion of silver nanoparticles with physical dispersal procedures, *Journal of Materials Processing Technology*, Volume 206, Issues 1-3, 2008, Pages 56-61
12. Thess A.; Lee R., Nikolaev P., Dai H., Petit P., Robert J., Xu C., Lee H., Kim S., Rinzler A., Colbert D., Scuseria G., Tomanek D, Fischer J., Smalley R., Crystalline ropes of metallic carbon nanotubes, *Science*, 1996 Vol.273, 483–488
13. Sang-ha Hwang, Young-Bin Park, Kwan Han Yoon and Dae Suk Bang, Smart Materials and Structures Based on Carbon Nanotube Composites in book *Carbon Nanotubes-synthesis, characterization, application*, Publisher by InTech 2011 Edited by: Siva Yellampalli, pp. 371-396
14. Awasthi K.; Kamalakaran R., Singh A., Srivastava O., Ball-milled carbon and hydrogen storage. *Int. J. Hydrog. Energy*, 2004, Vol.27 (4) 425–32
15. Jia, Z.; Wang Z., Liang J., Wei B. and Wu D. Production of short multi-walled carbon nanotubes. *Carbon*, Vol.37 (6), (1999) 903–906
16. Thostenson E. T. & Chou T.-W. (2006). Processing-structure-multi-functional property relationship in carbon nanotube/epoxy composites. *Carbon*, 2006 Vol.44 (14) 3022–3029
17. <http://www.exakt.de/EXAKT-Three-Roll-Mil.39+M52087573ab0.0.html>